Hexcel 8552 AS4 Unidirectional Prepreg Qualification Statistical Analysis Report

FAA Special Project Number SP4614W-HQ

Report Release Date: October 26, 2011

Report # NCP-RP-2010-008 Rev D

Elizabeth Clarkson, Ph.D.
National Center for Advanced Materials Performance (NCAMP)
National Institute for Aviation Research
Wichita State University
Wichita, KS 67260-0093

Testing Facility:
National Institute for Aviation Research
Wichita State University
1845 N. Fairmount
Wichita, KS 67260-0093

REVISIONS:

E1(sl(A)-1(i)z6(p)a0(Sb)2(et1(i)h C(at)l(A)a0(Sr)3(k-2(s)-2((d)]TJ ET Q q 110.4

Rev	By	Date	Rev App By	Pages Revised or Added

Table of Contents

1. Introduction 9

1.1 Symbols and Abbreviations 11

1.2 Pooling Across Environments 12

1.3 Basis Value Computational Process 12

1.4 Modified Coefficient of Variation (CV) Method 12

2. Background 14

2.1 ASAP Statistical Formulas and Computations 14
2.1.1 Basic Descriptive Statistics 14
2.1.2 Statistics for Pooled Data 14
2.1.3 Basis Value Computations 15
2.1.4 Modified Coefficient of Variation 16
2.1.5 Determination of Outliers 17
2.1.6 The k-Sample Anderson Darling Test for batch equivalency 18
2.1.7 The Anderson Darling Test for Normality 19
2.1.8 Levene's test for Equality of Coefficient of Variation 20

2.2 STAT-17 20
2.2.1 Distribution tests 21
2.2.2 Computing Normal Distribution Basis values 21
2.2.3 Non-parametric Basis Values 25
2.2.4 Non-parametric Basis Values for small samples 26
2.2.5 Analysis of Variance (ANOVA) Basis Values 28

2.3 Single Batch and Two Batch estimates using modified CV 30

2.4 Lamina Variability Method (LVM) 30

2.5 0º Lamina Strength Derivation 32
2.5.1 0º Lamina Strength Derivation (Alternate Formula) 32

3. Summary of Results 34

3.1 NCAMP Recommended B-basis Values 34

3.2 Lamina and Laminate Summary Tables 37

4. Lamina Test Results, Statistics, Basis Values and Graphs 39

4.1 Longitudinal (0º) Tension Properties (LT) 40

4.2 Trans º) Tension Properties (TT) 43
4.3 Longitudinal (0º) Compression Properties (LC) 45
4.4 Transverse (90º) Compression P roperties (TC) 47
4.5 In-Plane Shear Properties (IPS) 49
4.6 Short Beam Strength (SBS) Data 52
4.7 Unnotched Tension Properties (UNT0) 54
4.8 Unnotched Compression Properties (UNC0) 56
5. Laminate Test Results, Statistics, Basis Values and Graph 58
5.1 Quasi Isotropic Unnotched Tension Properties (UNT1) 58
5.2 “Soft” U nnotched Tension Properties (UNT2) 60
5.3 “Hard” Unnotched Tension Properties (UNT3) 62
5.4 Quasi Isotropic Unnotched Compressi n 1 (UNC1) 64
5.5 “Soft” Unnotched Compression (UNC2) ..... -7(on ( )3)Ts-75(ch5(OHm [1)n)2

5.18 “Hard” Filled Hole Compression (FHC3) 90
5.19 Laminate Short Beam Shear Strength (LSBS) Data 92
5.20

List of Tables

Table 1-1: Test Property Abbreviations 11
Table 1-2: Test Property Symbols 11
Table 1-3: Environmental Conditions Abbreviations 11
Table 2-1: K factors for normal distribution 22
Table 2-2: Weibull Distribution Basis Value Factors 24
Table 2-3: B-Basis Hans 643.44(d (..J 0 Tc 0 Tw 3[illegible]

Table 5-15: Statistics and Basis Values for OHT3 Strength data 75
Table 5-16: Statistics and Basis Values for FHT1 Strength data 77
Table 5-17: Statistics and Basis Values for FHT2 Strength data 79
Table 5-18: Statistics and Basis Values for FHT3 Strength data 81
Table 5-19: Statistics and Basis Values for OHC1 Strength data 83
Table 5-20: Statistics and Basis Values for OHC2 Strength data 85
Table 5-21: Statistics and Basis Values for OHC3 Strength data 87
Table 5-22: Statistics and Basis Values for FHC1 Strength data 88
Table 5-23: Statistics and Basis Values for FHC2 Strength data 89
Table 5-24: Statistics and Basis Values for FHC3 Strength data 91
Table 5-25: Statistics and Basis Values for LBS data as measured 93
Table 5-26: Statistics and Basis Values for SSB1 Strength data 95
Table 5-27: Statistics and Basis Values for SSB2 Strength data 97
Table 5-28: Statistics and Basis Values for SSB3 Strength data 99
Table 5-29: Statistics for ILT and CBS as measured data 100
Table 5-30: Statistics for Compression After Impact Strength data 101
Table 6-1: List of outliers 103

1. Introduction

This report contains statistical analysis of Hexcel 8552 AS4 Unidirectional prepreg at 190 gsm & 35% RC qualification data. Material property data is published in NCAMP Test Report CAM-RP-2010-002. The lamina and laminate material property data have been generated with FAA oversight through FAA Special Project Number SP 4614WI-Q and also meet the requirements outlined in NCAMP Standard Operating Procedure NSP 100. Test panels, test specimens, and test setups have been conformed by the FAA and the testing has been witnessed by the FAA.

B-Basis values, A-estimates, and B-estimates were calculated using a variety of techniques that are detailed in section two. The qualification material was procured to NCAMP Material Specification NMS 128/1 Rev – Initial Release dated February 6, 2007. The qualification test panels were cured in accordance with NCAMP Process Specification 81228 Cure “M,” June 7, 2007. The panels were fabricated by Cessna Aircraft Company, 5800 E. Pawnee, Wichita, KS 67218. The NCAMP Test Plan NTP 1628Q1 Rev. B was used for this qualification program. The testing was performed at the National Institute for Aviation Research (NIAR) in Wichita, Kansas.

The panels were fabricated by Cessna Aircraft Company, 5800 E Pawnee, Wichita, KS 67218 and cured in accordance with Baseline Cure Cycle (M) of NCAMP Process Specification NPS 81228 Rev A. The NCAMP Test Plan NTP 1128Q1 was used for this qualification program. The testing was performed at the National Institute for Aviation Research (NIAR) in Wichita, Kansas.

Basis numbers are labeled as ‘values’ when the data meets all the requirements of the working draft CMH-17 Revision G. When those requirements are not met, they will be labeled as ‘estimates’. When the data does not meet the requirements, the failure to meet these requirements is reported along with the specific requirement(s) the data fails to meet. The method used to compute the basis value is noted for each basis value provided. Where appropriate, in addition to the traditional computational methods, values computed using the modified coefficient of variation method is also provided.

The material property data acquisition process is designed to generate basic material property data with sufficient pedigree for submission to Complete Documentation sections of Composite Materials Handbook 17 (

October 26, 2011

Tests with a number immediately after the abbreviation indicate the layup:

1 = “Quasi-Isotropic”
2 = “Soft”
3 = “Hard”

EX: OHT1 is an open hole tension test with a “Quasi-Isotropic” layup

Detailed information about the test methods and conditions used is given in NCAMP

$$\text{Pooled Std. Dev. } S_p = \sqrt{\frac{\sum_{i=1}^{k}(n_i - 1)S_i^2}{\sum_{i=1}^{k}(n_i - 1)}} \qquad \text{Equation 4}$$

Where k refers to the number of batches and n_i refers to the number of specimens in the i^{th} sample.

2.1.2.2 Pooled Coefficient of Variation

Since the mean for the normalized data i

$$N = \sum_{j=1}^{r} n_j$$

$$f = N - r$$

Where F_0 is the standard normal distribution function. The observed significance level (OSL) is

$$OSL = \frac{1}{1 + e^{-0.48 + 0.78\ln(AD^*) + 4.58AD^*}}, \quad AD^* = \left(1 + \frac{0.2}{\sqrt{n}}\right)AD \qquad \text{Equation 31}$$

This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if, in fact, the data are a sample from a normal population. If OSL > 0.05, the data is considered sufficiently close to a normal distribution.

2.1.8

2.2.1 Distribution tests

In addition to testing for normality using the Anderson-Darling test (see 2.1.7); Stat17 also tests to see if the Weibull or Lognormal distribution is a good fit for the data.

Each distribution is considered using the Anderson-Darling test statistic which is sensitive to discrepancies in the tail regions. The Anderson-Darling test compares the cumulative distribution function for the distribution of interest with the cumulative distribution function of the data.

An observed significance level (OSL) based on the Anderson-Darling test statistic is computed for each test. The OSL measures the probability of observing an Anderson-Darling test statistic at least as extreme as the value calculated if the distribution under consideration is in fact the underlying distribution of the data. In other words, the OSL is the probability of obtaining a value of the test statistic at least as large as that obtained if the hypothesis that the data are actually from the distribution being tested is true. If the OSL is less than or equal to 0.05, then the assumption that the data are from the distribution being tested is rejected with at most a five percent risk of being in error.

If the normal distribution has an OSL greater than 0.05, then the data is assumed to be from a population with a normal distribution. If not, then if either the Weibull or lognormal distributions has an OSL greater than 0.05, then one of those can be used. If neither of these distributions has an OSL greater than 0.05, a non-parametric approach is used.

In what follows, unless otherwise noted, the sample size is denoted by n, the sample observations by $x_1, \ldots, x_n$

N	B-basis	A-basis
2	20.581	37.094
3	6.157	10.553
4	4.163	7.042
5	3.408	5.741
6	3.007	5.062
7	2.756	4.642
8	2.583	4.354
9	2.454	4.143
10	2.355	3.981
11	2.276	3.852
12	2.211	3.747
13	2.156	3.659
14	2.109	3.585
15	2.069	

In order to compute a check of the fit of a data set to the Weibull distribution and compute basis values assuming Weibull, it is first necessary to obtain estimates of the population shape and scale parameters (Section 2.2.2.3.1). Calculations specific to the goodness-of-fit test for the Weibull distribution are provided in section 2.2.2.3.2.

2.2.2.3.1 Estimating Weibull Parameters

This section describes the maximum likelihood method for estimating the parameters of the two parameter Weibull distribution. The maximum-likelihood estimates of the shape and scale parameters are denoted $\hat{\beta}$ and $\hat{\alpha}$. The estimates are the solution to the pair of equations:

2.2.2.3.3 Basis value calculations for the Weibull distribution

For the two-parameter Weibull distribution, the B-basis value is

$$B = \hat{q}e^{\left(-V/\hat{\beta}\sqrt{n}\right)} \quad \text{Equation 42}$$

where

$$\hat{q} = \hat{\alpha}(0.10536)^{1/\hat{\beta}} \quad \text{Equation 43}$$

To calculate the A-basis value, substitute the equation below for the equation above

$$\hat{q} \quad \hat{}(0.01005)^{1/}$$

The lognormal distribution is a positively skewed distribution that is simply related to the normal distribution. If something is lognormally distributed, then its logarithm is normally distributed. The natural (base e) logarithm is used.

2.2.2.4.1 Goodness-of-fit test for the Lognormal distribution

In order to test the goodness-of-fit of the lognormal distribution, take the logarithm of the data and perform the Anderson-Darling test for normality from Section 2.1.7. Using the natural logarithm, replace the linked equation above with linked equation below:

$$z_{(i)} = \frac{\ln\left(x_{(i)}\right) - \bar{x}_L}{s_L}, \quad \text{for } i = 1, \ldots, n \qquad \text{Equation 47}$$

where $x_{(i)}$ is the i^{th} smallest sample observation, $\bar{x}_L$ and s_L are the mean and standard deviation of the $\ln(x_i)$ values.

The Anderson-Darling statistic is then computed using the linked equation above and the observed significance level (OSL) is computed using the linked equation above. This OSL measures the probability of observing an Anderson-Darling statistic at least as extreme as the value calculated if in fact the data are a sample from a lognormal distribution. If OSL ≤ 0.05, one may conclude (at a five percent risk of being in error) that the population is not lognormally distributed. Otherwise, the hypothesis that the population is lognormally distributed is not rejected. For further information on these procedures, see reference 6.

2.2.2.4.2 Basis value calculations for the Lognormal distribution

If the data set is assumed to be from a population with a lognormal distribution, basis values are calculated using the equation above in section 2.1.3. However, the calculations are performed using the logarithms of the data rather than the original observations. The computed basis values are then transformed back to the original units by applying the inverse of the log transform.

2.2.3 Non-parametric Basis Values

Non-parametric techniques do not assume any particularly underlying distribution for the population the sample comes from. It does require that the batches be similar enough to be grouped together, so the ADK test must have a positive result. While it can be used instead of assuming the normal, lognormal or Weibull distribution, it typically results in lower basis values. One of following two methods should be used, depending on the sample size.

2.2.3.1 Non-parametric Basis Values for large samples

The required sample sizes for this ranking method differ for A and B basis values. A sample size of at least 29 is needed for the B basis value while a sample size of 299 is required for the A basis.

To calculate a B basis value for n > 28, the value of r is determined with the following formulas:

For B-basis values:

$$r_B = \frac{n}{10} - 1.645\sqrt{\frac{9n}{100}} + 0.23$$ Equation 48

For A-Basis values:

$$_A \quad \overline{100} \quad 1.645\sqrt{\frac{99}{10,000}} \quad 0.29 \quad \underline{19.1}$$

data and at least 55 data points. For a B-Basis value, there must be at least three batches represented in the data and at least 18 data points.

B-Basis Hanson-Koopmans Table		
n	r	k
2	2	35.177
3	3	7.859
4	4	4.505
5	4	4.101
6	5	3.064
7	5	2.858
8	6	2.382
9	6	2.253
10	6	2.137
11	7	1.897
12	7	1.814
13	7	1.738
14	8	1.599
15	8	1.540
16	8	1.485
17	8	1.434
18	9	1.354
19	9	1.311
20	10	1.253
21	10	1.218
22	10	1.184
23	11	1.143
24	11	1.114
25	11	1.087
26	11	1.060
27	11	1.035
28	12	1.010

The following calculations address batch-to-batch variability. In other words, the only grouping is due to batches and the sample Anderson-Darling test (Section 2.1.6) indicates that the batch to batch variability is too large to pool the data. The method is based on the two-way analysis of variance random-effects model, and the procedure is documented in reference 10.

ANOVA separates the total variation (called the sum of squares) of the data into two sources: between batch variation and within batch variation.

First, statistics are computed for each batch, which are indicated with a script ℓ sub

If u is less than one, it is set equal to one. The tolerance limit factor is

Denote the ratio of mean squares by $r = \frac{MSB}{MSE}$ Equation 59

The basis value is

$$T = \frac{k_0 - \frac{k_1}{\sqrt{n'}} + (k_0 - k_1)\sqrt{\frac{u}{u+n-1}}}{1 - \frac{1}{\sqrt{n'}}}$$ Equation 60

–
.

LVM Estimated B -Basis = $\bar{X}_1 - K_{(N_1,N_2)} \cdot \bar{X}_1 \cdot \max(CV_1, CV_2)$ Equation 62

When used in conjunction with the modified CV approach, a minimum value of 8% is used for the CV.

Mod CV LVM Estimated B -Basis = $\bar{X}_1 - K_{(N_1,N_2)} \cdot \bar{X}_1 \cdot \text{Max}(8\%, CV_1, CV_2)$ Equation 63

With:

$\bar{X}_1$ the mean of the laminate (small dataset)

N_1 the sample size of the laminate (small dataset)

N_2 the sample size of the lamina (large dataset)

CV_1 is the coefficient of variation of the laminate (small dataset)

CV_2 is the coefficient of variation of the lamina (large dataset)

$K_{(N_1,N_2)}$ is given in Table 2-5

	2	3	4	5	6	7	8	9	10	11	12	13	14	15
2	0	0	0	0	0	0	0	0	0	0	0	0	0	0
3	4.508	0	0	0	0	0	0	0	0	0	0	0	0	0
4	3.827	3.607	0	0	0	0	0	0	0	0	0	0	0	0
5	3.481	3.263	3.141	0	0	0	0	0	0	0	0	0	0	0
6	3.273	3.056	2.934	2.854	0	0	0	0	0	0	0	0	0	0
7	3.134	2.918	2.796	2.715	2.658	0	0	0	0	0	0	0	0	0
8	3.035	2.820	2.697	2.616	2.558	2.515	0	0	0	0	0	0	0	0
9	2.960	2.746	2.623	2.541	2.483	2.440	2.405	0	0	0	0	0	0	0
10	2.903	2.688	2.565	2.484	2.425	2.381	2.346	2.318	0	0	0	0	0	0
11	2.856	2.643	2.519	2.437	2.378	2.334	2.299	2.270	2.247	0	0	0	0	0
12	2.819	2.605	2.481	2.399	2.340	2.295	2.260	2.231	2.207	2.187	0	0	0	0
13	2.787	2.574	2.450	2.367	2.308	2.263	2.227	2.198	2.174	2.154	2.137	0	0	0
14	2.761	2.547	2.423	2.341	2.281	2.236	2.200	2.171	2.147	2.126	2.109	2.093	0	0
15	2.738	2.525	2.401	2.318	2.258	2.212	2.176	2.147	2.123	2.102	2.084	2.069	2.056	0
16	2.719	2.505	2.381	2.298	2.238	2.192	2.156	2.126	2.102	2.081	2.063	2.048	2.034	2.022
17	2.701	2.488	2.364	2.280	2.220	2.174	2.138	2.108	2.083	2.062	2.045	2.029	2.015	2.003
18	2.686	2.473	2.348	2.265	2.204	2.158	2.122	2.092	2.067	2.046	2.028	2.012	1.999	1.986
19	2.673	2.459	2.335	2.251	2.191	2.144	2.108	2.078	2.053	2.032	2.013	1.998	1.984	1.971
20	2.661	2.447	2.323	2.239	2.178	2.132	2.095	2.065	2.040	2.019	2.000	1.984	1.970	1.958
21	2.650	2.437	2.312	2.228	2.167	2.121	2.084	2.053	2.028	2.007	1.988	1.972	1.958	1.946
22	2.640	2.427	2.302	2.218	2.157	2.110	2.073	2.043	2.018	1.996	1.978	1.962	1.947	1.935
23	2.631	2.418	2.293	2.209	2.148	2.101	2.064	2.033	2.008	1.987	1.968	1.952	1.938	1.925
24	2.623	2.410	2.285	2.201	2.139	2.092	2.055	2.025	1.999	1.978	1.959	1.943	1.928	1.916
25	2.616	2.402	2.277	2.193	2.132	2.085	2.047	2.017	1.991	1.969	1.951	1.934	1.920	1.907

2.5 0º Lamina Strength Derivation

Lamina strength values in the 0º direction were not obtained directly for any conditions during compression tests. They are derived from the cross-ply laminate test results using a back out formula. Unless stated otherwise, the 0° lamina strength values were derived using the following formula:

$F_0^u = F_{0/90}^u \cdot BF$ where BF is the backout factor.

$F_{0/90}^u$ = UNC0 or UNT0 strength value

$$BF = \frac{E_1\left[V_0 E_2 + (1-V_0)\, E_1\right] - (\nu_1\, E_{22})^2}{\left[V_0 E_1 + (1-V_0)\, E_2\right]\left[V_0 E_2 + (1-V_0)\, E_1\right] - (\nu_1\, E_{22})^2} \qquad \text{Equation 64}$$

V_0 = fraction of 0º plies in the cross-ply laminate (½ for UNT0 and 1/3 for UNC0)
E_1 = Average across of batches of modulus for LC and LT as appropriate
E_2 = Average across of batches of modulus for TC and TT as appropriate
ν_{12} = major Poisson's ratio of 0º plies from an average of all batches

This formula can also be found in the Composite Materials Handbook (working draft CMH-17 Rev G) in section 2.4.2, equation 2.4.2.1(b).

In computing these strength values, the values for each environment are computed separately. The compression values are computed using only compression data, the tension values are computed using only tension data. Both normalized and as measured computations are done using the as measured and normalized strength values from the UNC0 and UNT0 strength values.

2.5.1 0º Lamina Strength Derivation (Alternate Formula)

In some cases, the previous formula cannot be used. For example, there were no ETD tests run for transverse tension and compression, so the value for E_2 was not available. In that case, an alternative formula is used to compute the strength values for longitudinal tension and compression. It is similar to, but not quite the same as the formula detailed above. It requires the UNC0 and UNT0 strength and modulus data in addition to the LC and LT modulus data.

The 0° lamina strength values for the LC ETD condition were derived using the formula:

$$F_0^{cu} = F_{0/90}^{cu}\,\frac{E_1^c}{E_{0/90}^c}, \quad F_0^{tu} = F_{0/90}^{tu}\,\frac{E_1^t}{E_{0/90}^t} \qquad \text{Equation 65}$$

with F_0^{cu}, F_0^{tu} the derived mean lamina strength value for compression and tension respectively

$F_{0/90}^{cu}$, $F_{0/90}^{tu}$ are the mean strength values for UNC0 and UNT0 respectively

E_1^c, E_1^t are the modulus values for LC and LT respectively

$E_{0/90}^c$, $E_{0/90}^t$ are the modulus values for UNC0 and UNT0 respectively

This formula can also be found in the Composite Materials Handbook (working draft CMH-17 Rev G) in section 2.4.2, equation 2.4.2.1(d).

3. Summary of Results

The basis values for all tests are summarized in the following tables. NCAMP recommended B-basis values meet all requirements of working draft CMH-17 Rev G. However, not all test data meets those requirements. The summary tables provide a complete listing of all computed basis values and estimates of basis values. Data that does not meet the requirements of working draft CMH-17 Rev G are shown in shaded boxes and labeled as estimates. Basis values computed with the modified coefficient of variation (CV) are presented whenever possible. Basis values and estimates computed without that modification are presented for all tests.

3.1 NCAMP Recommended B-basis Values

The following rules are used in determining what basis value, if any, is included in tables Table 3-1 and Table 3-2 of recommended values.

1. Recommended values are NEVER estimates. Only B-basis values that meet all requirements for publication in of working draft CMH-17 Rev G are recommended.
2. Modified CV basis values are preferred. Recommended values will be the modified CV basis value when available. The CV provided with the recommended basis value will be the one used in the computation of the basis value.
3. Only normalized basis values are given for properties that are normalized.
4. ANOVA B-basis values are not recommended since only three batches of material are available and working draft CMH-17 Rev G recommends that no less than five batches be used when computing basis values with the ANOVA method.
5. Caution is recommended with B-basis values calculated from STAT17 when the B-basis value is 90% or more of the average value. Basis values of 90% or more of the mean value imply that the CV is unusually low and may not be conservative. Such values will be indicated.
6. If the data appear questionable (e.g. when the CTD-ETW trend of the basis values are not consistent with the CTD-ETW trend of the average values), then the B-basis values will not be recommended.

October 26, 2011

4. Lamina Test Results, Statistics, Basis Values and Graphs

Test data for fiber dominated properties was normalized according to nominal cured ply thickness. Both normalized and as measured statistics were included in the tables, but only the normalized data values were graphed. Test failures, outliers and explanations regarding computational choices were noted in the accompanying text for each test.

All individual specimen results are graphed for each test by batch and environmental condition with a line indicating the recommended basis values for each environmental condition. The data is jittered (moved slightly to the left or right) in order for all specimen values to be clearly visible. The strength values are always graphed on the vertical axis with the scale adjusted to include all data values and their corresponding basis values. The vertical axis may not include zero. The horizontal axis values will vary depending on the data and how much overlapping of there was of the data within and between batches. When there was little variation, the batches were graphed from left to right and the environmental conditions were identified by the shape and color of the symbol used to plot the data. Otherwise, the environmental conditions were graphed from left to right and the batches were identified by the shape and color of the symbol.

When a dataset fails the Anderson-Darling k-sample (ADK) test for batch-to-batch variation an chn

4.1 Longitudinal (0°) Tension Properties (LT)

Longitudinal Tension Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	236.95	271.47	279.17	240.12	279.61	284.85
Stdev	7.52	11.21	8.58	7.87	12.64	10.29
CV	3.18	4.13	3.07	3.28	4.52	3.61
Mod CV	6.00	6.07	6.00	6.00	6.26	6.00
Min	218.94	252.71	262.58	222.91	255.04	263.16
Max	247.64	290.25	297.21	254.09	306.97	305.09
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	20	19	19	20
Basis Values and/or Estimates						
B-basis Value	220.78	255.29	263.07	221.79	261.29	266.62
A-estimate	209.94	244.46	252.22	209.52	249.02	254.33
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	209.13	243.64	251.48	211.35	250.84	256.22
A-estimate	190.49	225.00	232.81	192.08	231.57	236.93
Method	pooled	pooled	pooled	pooled	pooled	pooled

Table 4-1: Statistics and Basis values for LT strength computed from UNT0 specimens

Longitudinal Tension Modulus Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	18.17	18.46	18.76	18.48	19.09	19.00
Stdev	0.16	0.61	0.19	0.21	0.59	0.23
CV	0.91	3.28	1.03	1.16	3.07	1.20
Mod CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	17.94	16.29	18.34	18.18	18.29	18.60
Max	18.60	19.15	19.09	18.89	20.69	19.36
No. Batches	3	3	3	3	3	3
No. Spec.	19	21	24	19	21	24

Table 4-2: Statistics from LT modulus

The statistics and basis values for strength computed from the LT specimens are provided in Table 4-3. Pooling across environments was not acceptable because the RTD and ETW datasets did not pass the ADK test. ANOVA was the only appropriate method that could be used with those datasets and because there were only three batches, those values are considered to be estimates only. Estimates computed using the modified CV method are provided for the RTD environment but not the ETW environment due to the non-normality of the data from the ETW environment. Pooling across the environments was not acceptable due to the non-normality as well. These are termed estimates due to the failure of the ADK test after the transformation for the modified CV method.

There was one outlier, the lowest value in batch 2 of the RTD data, that was retained for this analysis. The data, B-estimates and B-basis values are shown graphically in Figure 4-2.

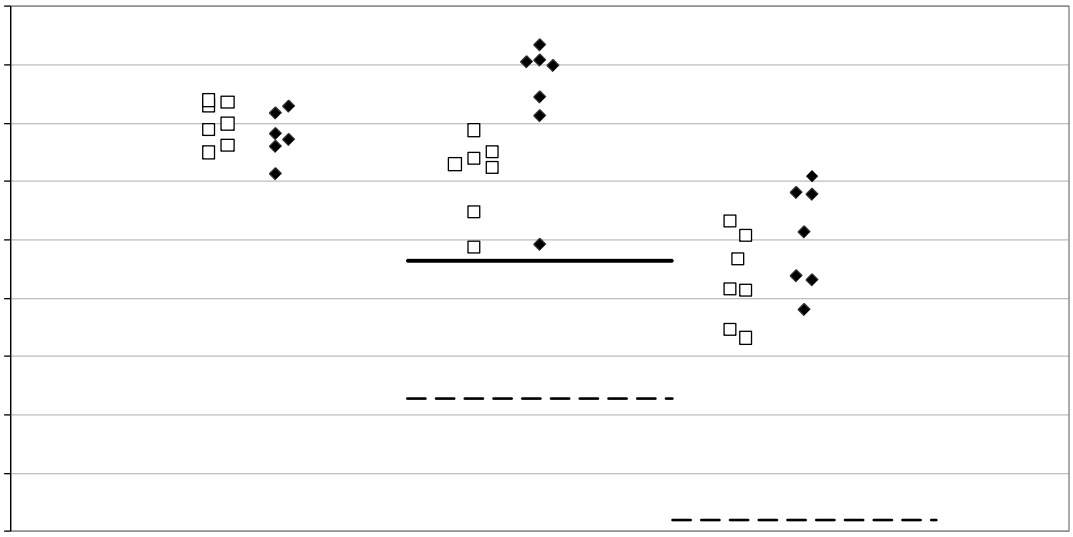

4.2 Transverse (90°) Tension Properties (TT)

Transverse Tension data is not normalized for unidirectional tape. The pooled batches failed Levene's test for equality of variance, so pooling across environments was not acceptable. CTD and RTD environments have data from only two batches because specimens from the third batch were removed due to deep scratches on those specimens. This means that only estimates are provided for the CTD and RTD environments. Due to the large CV of the CTD and RTD environments, modified CV basis values are not available. There were no outliers.

Statistics, estimates and basis values are given for strength data as measured in Table 4-4 and for the modulus data as measured in Table 4-5. The data, B-estimates and the B-basis values are shown graphically in Figure 4-3.

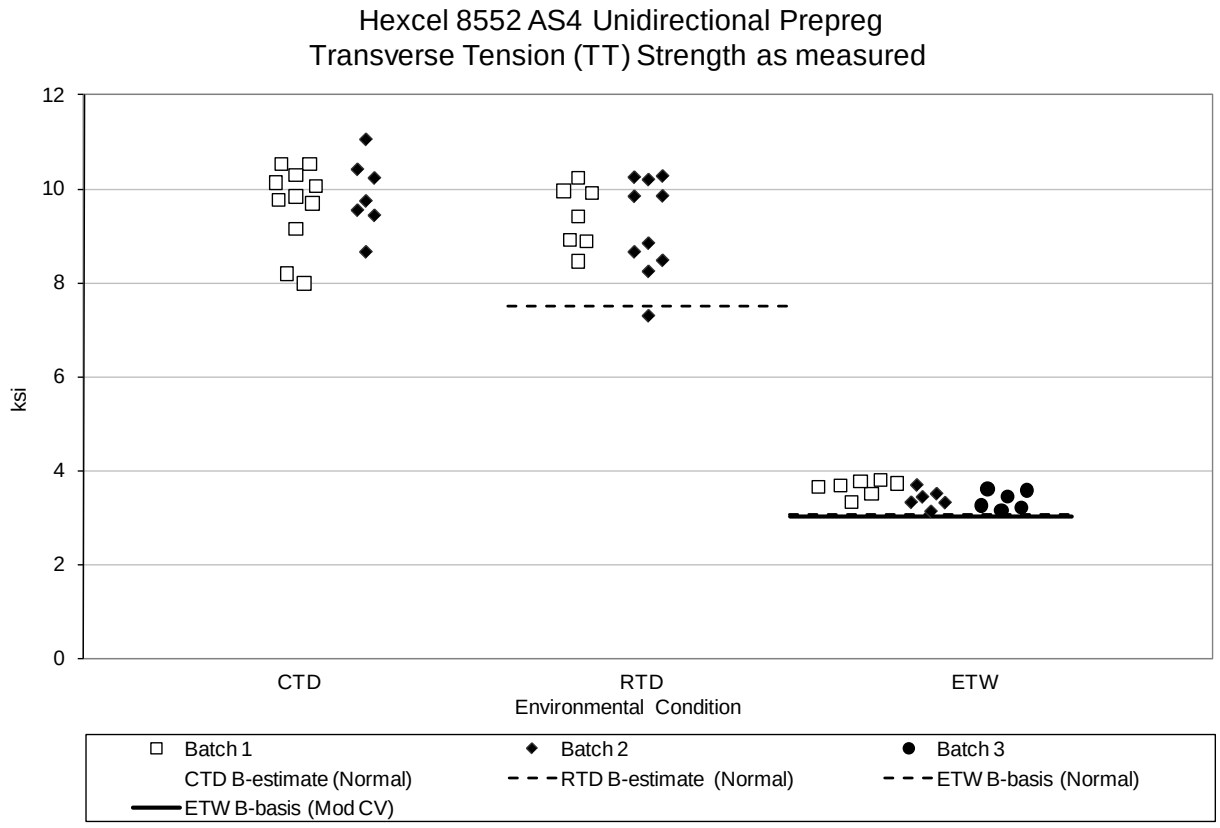

Figure 4-3: Batch Plot for TT strength as measured

4.3 Longitudinal (0°) Compression Properties (LC)

The strength values for 0° properties are computed via the formulas specified in section 2.5. For the CTD, RTD and ETW condition, equation 64 was used. For the ETD values, a different formula was required because there were no specimens tested in that condition for the transverse compression and the modulus value of TC is needed to use the same formula as was used for the

Longitudinal Compression Strength Basis Values and Statistics

	Normalized				As Measured			
Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	247.73	202.70	218.47	150.22	252.51	215.29	220.63	158.78
Stdev	14.84	9.26	8.45	11.09	15.38	11.93	8.57	13.26
CV	5.99	4.57	3.87	7.38	6.09	5.54	3.89	8.35
Mod CV	7.00	6.28	6.00	7.69	7.05	6.77	6.00	8.35
Min	223.33	180.82	202.38	135.75	229.71	195.02	204.26	138.68
Max	270.64	217.67	237.20	175.96	280.80	242.42	238.24	181.42
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	15	20	18	21	15	20	18	21
Basis Value Estimates								
B-basis Value	228.28	183.83	199.40	131.44	230.46	193.89	199.00	137.48
A-Estimate	215.77	171.23	186.83	118.82	216.27	179.61	184.75	123.18
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Value Estimates								
B-basis Value	223.63	179.31	194.84	126.94	226.53	190.08	195.15	133.69
A-Estimate	208.12	163.70	179.26	111.31	209.82	173.25	178.36	116.84
Method	pooled	pooled	pooled	pooled	pooled	pooled	pooled	pooled

4.4 Transverse (90º) Compression Properties (TC)

Transverse Compression data is not normalized for unidirectional tape. The pooled data fails Levene's test for equality of variance, so the data cannot be pooled across environments. The data for the RTD environment failed the ADK test, so only the ANOVA method could be used to compute basis values. Since there are only three batches available, this means that basis values computing using the ANOVA method are estimates only. However, the RTD data passed the ADK test after applying the modified CV transformation so modified CV basis values are provided for that environment. There were no outliers.

Statistics, basis values and estimates are given for strength data in Table 4-8 and for the modulus data in Table 4-9. The data, B-estimates and the B-basis values are shown graphically in Figure 4-5.

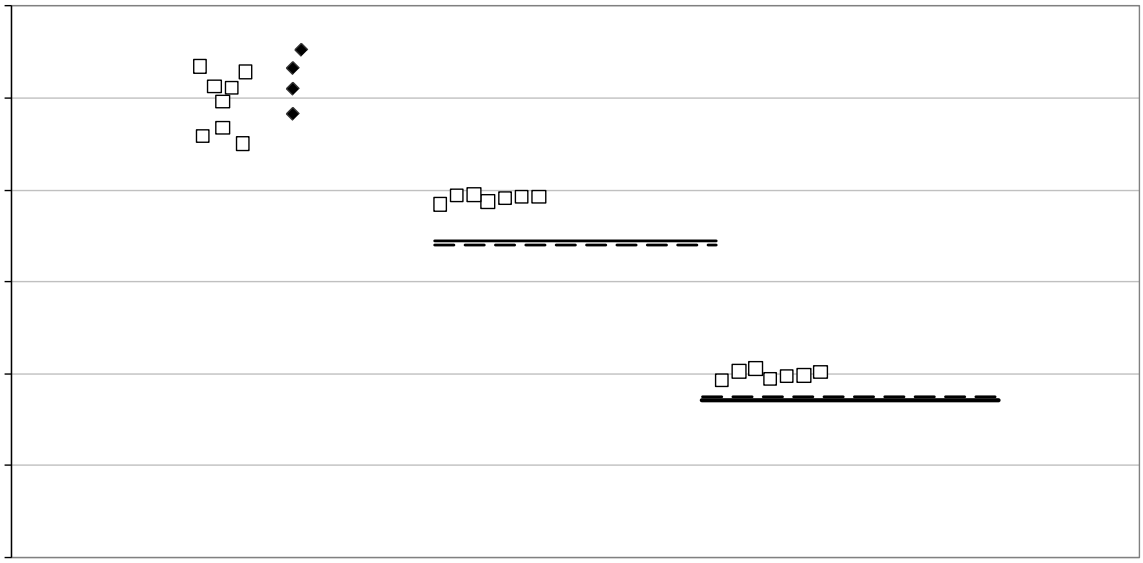

Transverse Compression Strength Basis Values and Statistics			
As Measured			
Env	CTD	RTD	ETW
Mean	51.49	38.85	19.71
Stdev	3.22	0.91	1.17
CV	6.25	2.35	5.94
Mod CV	7.13	6.00	6.97
Min	45.06	37.22	17.77
Max	56.60	40.64	22.42
No. Batches	3	3	3
No. Spec.	20	19	19
Basis Values and/or Estimates			
B-basis Value	45.29		17.43
B-estimate		34.07	
A-estimate	40.88	30.65	15.81
Method	Normal	ANOVA	Normal
Modified CV Basis Values and/or Estimates			
B-basis Value	44.42	34.31	17.03
A-estimate	39.40	31.09	15.13
Method	normal	normal	normal

Table 4-8: Statistics and Basis Values for TC Strength data as measured

Transverse Compression Modulus Statistics			
	As Measured		
Env	CTD	RTD	ETW
Mean	1.56	1.43	1.14
Stdev	0.06	0.04	0.08
CV	3.55	2.94	6.59
Mod CV	6.00	6.00	7.30
Min	1.46	1.37	1.04
Max	1.65	1.50	1.31
No. Batches	3	3	3
No. Spec.	20	19	19

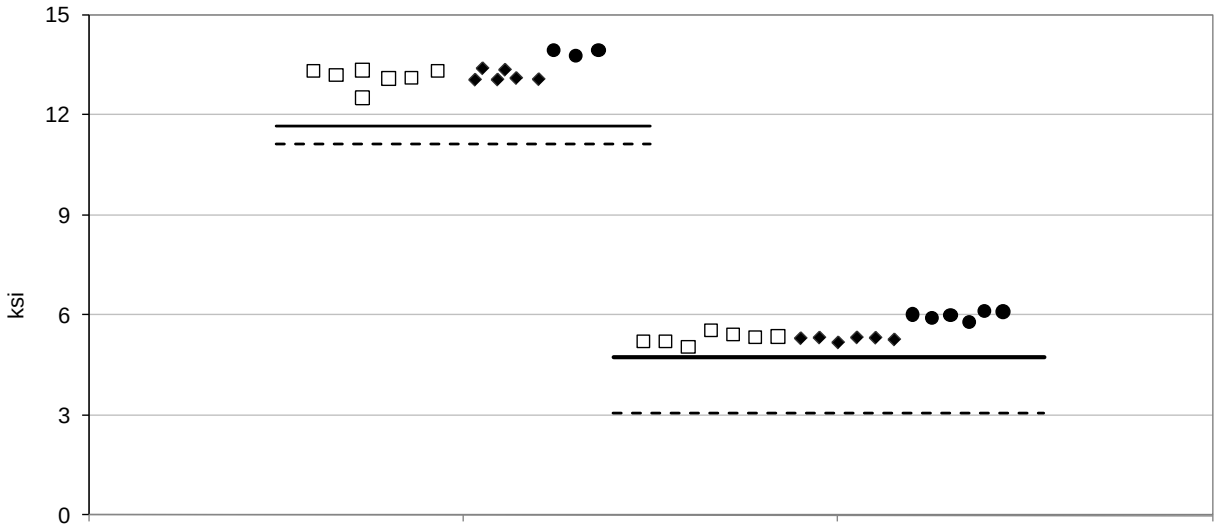
15
12
9
6
3
0
ksi

In Plane Shear Modulus Statistics		
As measured		
CTD	RTD	ETW
0.81	0.70	0.34
0.02	0.02	0.02
2.37	3.41	5.03
6.00	6.00	6.51
0.79	0.66	0.32
0.85	0.75	0.39
3	3	3
20	22	19

4.6 Short Beam Strength (SBS) Data

The Short Beam Shear data is not normalized. The ETD and ETW environmental data failed the ADK test, s9nvi 3-6(.6)]T7 m

Short Beam Shear (SBS) Strength (ksi) Basis Values and Statistics				
As Measured				
Env	CTD	RTD	ETD	ETW
Mean	20.87	16.63	10.95	8.25
Stdev	0.59	0.28	0.27	0.29
CV	2.82	1.68	2.50	3.52
Mod CV	6.00	6.00	6.00	6.00
Min	19.61	16.12	10.60	7.65
Max	21.87	17.06	11.68	8.60
No. Batches	3	3	3	3
No. Spec.	24	19	19	19
Basis Values and/or Estimates				
B-basis Value	19.78	16.09		
B-estimate			9.92	6.70
A-estimate	19.00	15.70	9.19	5.59
Method	Normal	Normal	ANOVA	ANOVA
Modified CV Basis Values and/or Estimates				
B-basis Value	19.30	15.03	9.35	6.65
A-estimate	18.24	13.98	8.29	5.59
Method	pooled	pooled	pooled	pooled

Table 4-12: Statistics and Basis Values for SBS data as measured

4.7 Unnotched Tension Properties (UNT0)

There were no outliers or test failures. Pooling across environments was permissible. Statistics basis values and estimates are given for strength data in Table 4-13 and for the modulus data in Table 4-14. The normalized data and the basis values are shown graphically in Figure 4-9.

Unnotched Tension (UNT0) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	128.14	145.45	145.54	129.69	149.48	148.42
Stdev	4.07	6.01	4.47	4.25	6.76	5.36
CV	3.18	4.13	3.07	3.28	4.52	3.61
Modified CV	6.00	6.07	6.00	6.00	6.26	6.00
Min	118.40	135.40	136.89	120.40	136.34	137.12
Max	133.92	155.51	154.94	137.24	164.11	158.97
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	20	19	19	20
Basis Values and/or Estimates						
B-basis Value	119.52	136.83	136.96	119.96	139.75	138.74
A-estimate	113.75	131.06	131.18	113.44	133.23	132.21
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	113.35	130.65	130.82	114.42	134.21	133.22
A-estimate	103.44	120.75	120.89	104.19	123.97	122.98
Method	pooled	pooled	pooled	pooled	pooled	pooled

4.8 Unnotched Compression Properties (UNC)

There were no test failures or outliers. Statistics, basis values and estimates are given for strength data in Table 4-15 and for the modulus data in Table 4-16. The normalized data and the B-basis values are shown graphically in Figure 4-10.

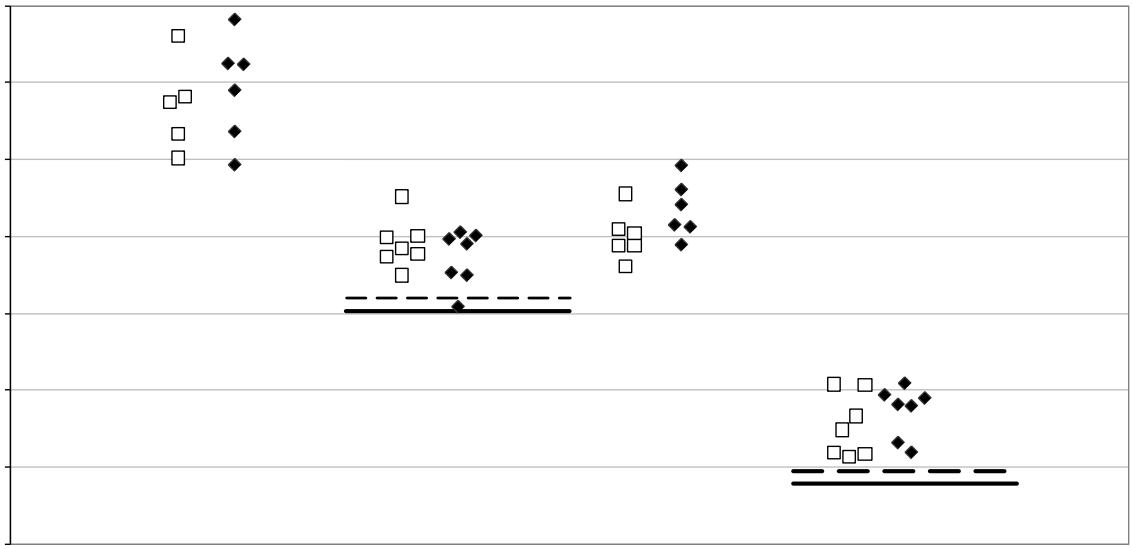

Env	CTD	RTD	ETD	ETW	CTD	RTD	ETD	ETW
Mean	99.02	79.36	82.13	56.86	100.79	83.85	83.69	59.95
Stdev	5.93	3.63	3.18	4.20	6.14	4.65	3.25	5.00
CV	5.99	4.57	3.87	7.38	6.09	5.54	3.89	8.35
Modified CV	7.00	6.28	6.00	7.69	7.05	6.77	6.00	8.35
Min	89.26	70.79	76.08	51.38	91.69	75.96	77.48	52.36
Max	108.17	85.22	89.17	66.60	112.08	94.42	90.37	68.50
No. Batches	3	3	3	3	3	3	3	3
No. Spec.	15	20	18	21	15	20	18	21

5. Laminate Test Results, Statistics, Basis Values and Graph

5.1 Quasi Isotropic Unnotched Tension Properties (UNT1)

The data from the ETW environment failed the ADK test, so only the ANOVA method could be used to compute basis values. Since there are only three batches available, this means that basis values computing using the ANOVA method are estimates only. However, the ETW data passed the ADK test with the modified CV transform, so modified CV basis values are provided. The pooled data failed Levene's test, so pooling across environments was not appropriate.

There were three outliers altogether, two in the as measured data and the third outlier in the normalized data. In the as measured data, one outlier was on the low side of batch 3 in the CTD environment and the other outlier was on the low side of batch 2 in the ETW environment. The outlier in the normalized data was on the high side of batch 2 in the CTD environment. All three were outliers before, but not after, pooling the three batches for their respective environments. All three outliers were retained for this analysis.

Statistics, basis values and estimates are given for UNT strength data in Table 5-1 and for the modulus data in Table 5-2. The normalized data B-estimates and B-basis values are shown graphically in Figure 5-1.

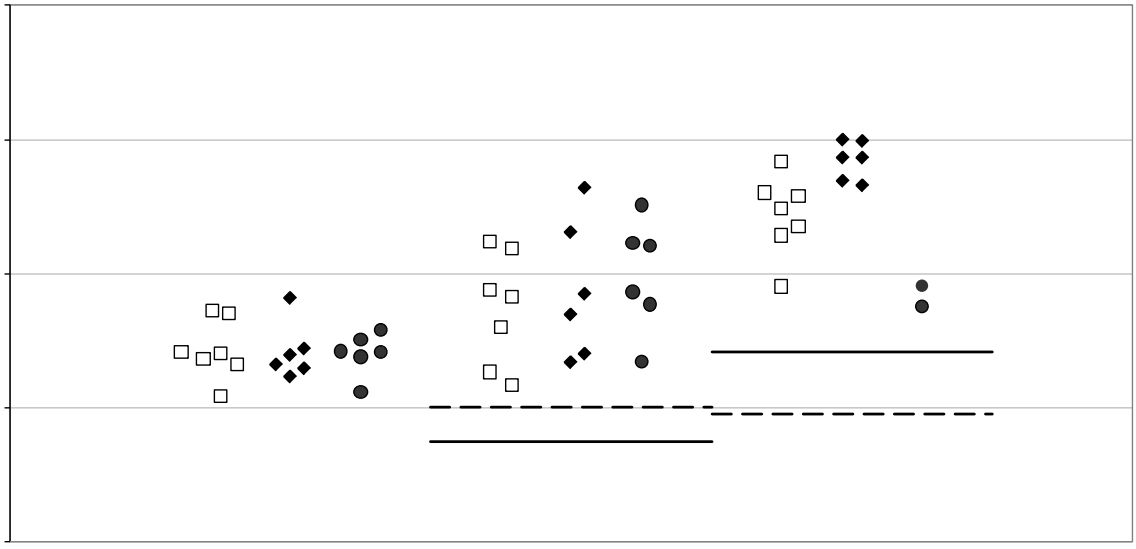

Unnotched Tension (UNT1) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	84.21	88.61	95.18	85.14	90.09	95.91
Stdev	1.89	4.35	3.62	1.98	3.76	3.64
CV	2.24	4.91	3.80	2.33	4.17	3.80
Modified CV	6.00	6.45	6.00	6.00	6.09	6.00
Min	80.88	81.73	87.53	81.70	83.50	88.21
Max	88.20	96.39	99.96	89.81	96.03	100.76
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	20	19	19	20
Basis Values and/or Estimates						
B-basis Value	80.53	80.13		81.28	82.77	
B-estimate			79.56			79.67
A-estimate	77.91	74.12	68.42	78.53	77.56	68.09
Method	Normal	Normal	ANOVA	Normal	Normal	ANOVA
Modified CV Basis Values and/or Estimates						
B-basis Value	74.36	77.46	84.18	75.18	79.41	84.82
A-estimate	67.38	69.56	76.36	68.12	71.83	76.94
Method	normal	normal	normal	normal	normal	normal

Unnotched Tension (UNT2) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	66.61	63.62	48.17	67.21	64.14	48.37
Stdev	2.00	1.24	1.82	1.71	1.01	1.92
CV	3.00	1.95	3.79	2.54	1.57	3.96
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	61.11	61.25	43.93	62.36	62.78	43.13
Max	69.66	65.91	50.26	69.84	66.24	50.51
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19
Basis Values and/or Estimates						
B-basis Value	59.58	61.20		63.88	62.17	
B-estimate			41.18			40.23
A-estimate	50.68	59.49	36.20	61.51	60.77	34.42
Method	Non-parametric	Normal	ANOVA	Normal	Normal	ANOVA
Modified CV Basis Values and/or Estimates						
B-basis Value	60.29	57.30	41.85	59.35	56.64	42.72
A-estimate	56.06	53.07	37.61	53.78	51.32	38.71
Method	pooled	pooled	pooled	normal	normal	normal

Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	149.38	152.32	144.59	151.36	154.86	145.49

5.5 "Soft" Unnotched Compression (UNC2)

The normalized RTD data did not pass the test for normality, but the pooled data set did, so pooling the two environments is acceptable. There was one outlier, it was in the normalized RTD environment. It was on the low side of batch three. It was an outlier only for batch three, not for the three RTD batches pooled together. It was retained for this analysis.

Statistics, basis values and estimates are given for UNC2 strength data in Table 5-5 and for the modulus data in Table 5-6. The normalized data and the basis values are shown graphically in Figure 5-5.



Unnotched Compression (UNC2) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	62.42	45.60	65.39	46.55
Stdev	2.60	2.49	3.00	2.78
CV	4.17	5.46	4.58	5.97
Modified CV	6.08	6.73	6.29	6.99
Min	55.87	42.20	59.18	42.76
Max	65.53	51.58	69.42	53.58
No. Batches	3	3	3	3
No. Spec.	19	22	19	22
Basis Values and/or Estimates				
B-basis Value	57.87	41.11	60.22	41.45
A-estimate	54.77	37.99	56.71	37.92
Method	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates				
B-basis Value	56.28	39.54	58.80	40.05
A-estimate	52.11	35.35	54.32	35.55
Method	pooled	pooled	pooled	pooled

Table 5-9: Statistics and Basis Values for UNC2 Strength data

Unnotched Compression (UNC2) Modulus				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	4.30	3.84	4.51	3.93
Stdev	0.13	0.10	0.14	0.11
CV	3.08	2.69	3.05	2.69
Modified CV	6.00	6.00	6.00	6.00
Min	4.03	3.67	4.14	3.71
Max	4.49	4.01	4.72	4.11
No. Batches	3	3	3	3
No. Spec.	19	19	19	19

Unnotched Compression (UNC3) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	131.05	88.01	134.64	89.16
Stdev	4.96	6.04	6.11	5.76
CV	3.79	6.86	4.54	6.46
Modified CV	6.00	7.43	6.27	7.23
Min	123.68	78.03	124.11	78.81
Max	140.28	102.09	146.13	101.71
No. Batches	3	3	3	3
No. Spec.	19	21	19	21
Basis Values and/or Estimates				
B-basis Value	121.08	78.12	123.99	78.61
A-estimate	114.28	71.31	116.74	71.33
Method	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates				
B-basis Value	118.13	75.20	121.24	75.88
A-estimate	109.32	66.37	112.12	66.73
Method	pooled	pooled	pooled	pooled

Table 5-11: Statistics and Bt stics and

5.7 Quasi Isotropic Open Hole Tension Properties (OHT1)

The data from the ETW environment, both normalized and as measured, did not pass the test for normality. However, the pooled dataset did pass the normality test, so pooling the three environments is acceptable.

There were three outliers altogether. One outlier in the RTD condition for the as measured data

Open Hole Tension (OHT1) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	45.05	47.63	51.68	45.27	47.84	51.79
Stdev	1.23	1.33	1.68	1.25	1.45	1.80
CV	2.74	2.79	3.26	2.76	3.04	3.48
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	41.95	44.91	49.09	43.34	44.86	48.62
Max	46.87	49.64	57.02	47.29	49.85	56.81
No. Batches	3	3	3	3	3	3
No. Spec.	20	19	22	20	19	22
Basis Values and/or Estimates						
B-basis Value	42.55	45.11	49.20	42.60	45.16	49.14
A-estimate	40.86	43.43	47.51	40.81	43.37	47.35
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	40.01	42.56	46.68	40.20	42.75	46.77
A-estimate	36.61	39.17	43.28	36.80	39.35	43.35
Method	pooled	pooled	pooled	pooled	pooled	pooled

5.8 “Soft”

5.9 “Hard” Open Hole Tension Properties (OHT3)

There were no test failures, so pooling across environments was acceptable. There were no outliers. Statistics

5.10 Quasi Isotropic Filled Hole Tension (FHT1)

Only the normalized RTD data passes the ADK test for batch to batch variation, so only the ANOVA method could be used to compute basis values for all other datasets. Since there are only three batches available, this means that basis values computing using the ANOVA method are estimates only. However, all the datasets passed the ADK test with the modified CV transform, so modified CV basis values are provided, but pooling across environments was not appropriate for the normalized data due to a normality test failure of the transformed data.

There was one outlier. In was on the high side of batch two in the as measured ETW dataset. It was not an outlier in the normalized ETW dataset. It was an outlier only after pooling the three batches of ETW data. It was retained for this analysis.

Statistics, basis values and estimates are given for FHT1 strength data in Table 5-16. The normalized data, B-estimates and B-basis values are shown graphically in Figure 5-10 .

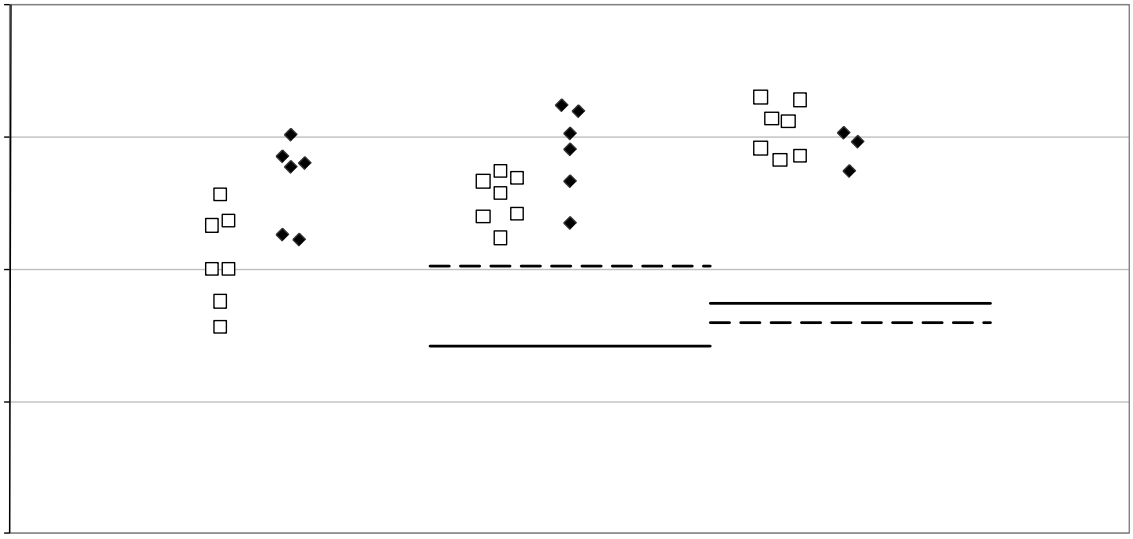

5.11 "Soft" Filled Hole Tension (FHT2)

The FHT2 data had no test failures or outliers. Pooling across environments was acceptable. Statistics, basis values and estimates are given for FHT2 strength data in Table 5-17. The normalized data and the B-basis values are shown graphically in Figure 5-11.

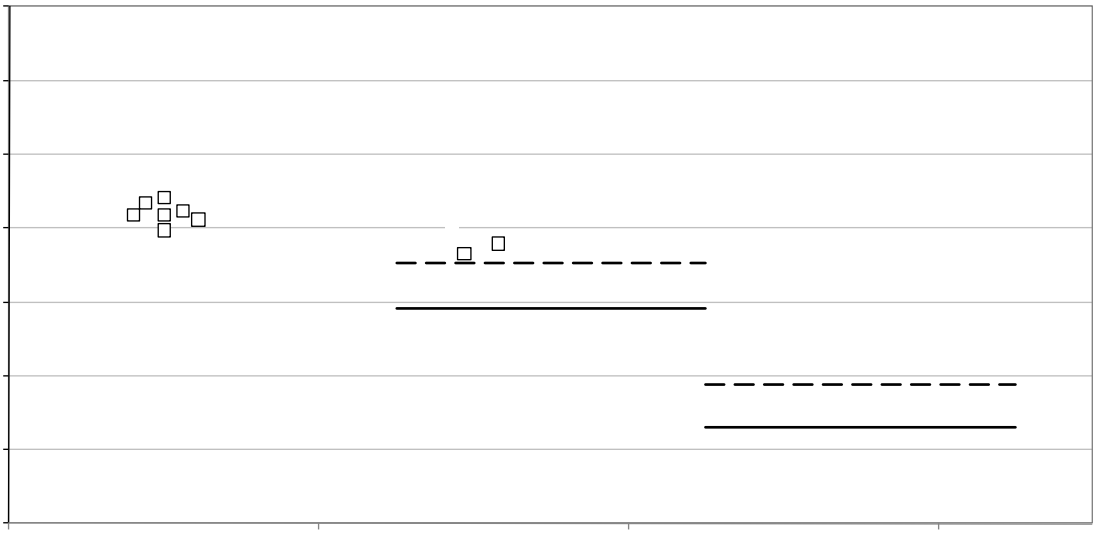

Filled-Hole Tension (FHT2) Strength Basis Values and Statistics

	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	45.86	44.08	35.93	46.72	44.65	36.46
Stdev	0.85	1.01	0.69	0.66	0.86	0.69
CV	1.86	2.29	1.92	1.41	1.91	1.89
Modified CV	6.00	6.00	6.00	6.00	6.00	6.00
Min	44.35	42.57	34.36	45.44	43.41	34.98
Max	47.28	46.62	36.77	47.96	46.70	37.43
No. Batches	3	3	3	3	3	3
No. Spec.	19	18	20	19	18	20
Basis Values and/or Estimates						
B-basis Value	44.36	42.58	34.44	45.43	43.36	35.17
A-estimate	43.35	41.57	33.44	44.56	42.49	34.30
Method	pooled	pooled	pooled	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	41.43	39.63	31.53	42.22	40.13	31.98
A-estimate	38.46	36.67	28.56	39.21	37.12	28.96
Method	pooled	pooled	pooled	pooled	pooled	pooled

5.12 “Hard”

Filled-Hole Tension (FHT3) Strength Basis Values and Statistics						
	Normalized			As Measured		
Env	CTD	RTD	ETW	CTD	RTD	ETW
Mean	65.96	74.02	78.30	67.78	75.29	79.37
Stdev	2.66	2.94	1.66	2.50	2.69	1.73
CV	4.04	3.98	2.12	3.68	3.58	2.19
Modified CV	6.02	6.00	6.00	6.00	6.00	6.00
Min	59.07	69.21	75.02	62.20	69.81	75.93
Max	69.46	79.63	81.30	72.05	79.83	82.71
No. Batches	3	3	3	3	3	3
No. Spec.	19	19	19	19	19	19
Basis Values and/or Estimates						
B-basis Value		68.28	75.07	63.66	71.18	75.25
B-estimate	54.60					
A-estimate	46.49	64.21	72.77	60.90	68.42	72.49
Method	ANOVA	Normal	Normal	pooled	pooled	pooled
Modified CV Basis Values and/or Estimates						
B-basis Value	58.28	66.33	70.61	59.95	67.47	71.54
A-estimate	53.12	61.18	65.46	54.71	62.22	66.30
Method	pooled	pooled	pooled	pooled	pooled	pooled

Open Hole Compression (OHC1) Strength Basis Values and OHetistics				
	Normlized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	47.28	33.09	47.82	33.46
Stdev	0.81	0.73	0.96	0.97
CV	1.72	2.19	2.00	2.91
Modified CV	6.00	6.00	6.00	6.00
Min	45.95	31.72	46.63	32.05
Max	48.61	34.61	49.72	35.52
No. Batches	3	3	3	3
No. Spec.	19	21	19	21
Basis Values and/or Estimates				
B-basis Value	45.90	31.73	46.38	31.60
A-estimate	44.96	30.78	42.54	30.28
Method	pooled	pooled	Non-parametric	Normal
Modified CV Basis Values and/or Estimtes				
B-basis Value	42.92	28.77	42.23	29.63
A-estimate	39.95	25.79	38.26	26.91
Method	pooled	pooled	normal	normal

5.14 "Soft" Open Hole Compression (OHC2)

The as measured data from the RTD environment failed the normality test, but the as measured pooled data was acceptably normal, so pooling was appropriate for the as measured dataset. Despite the data from both environments passing the normality test individually, the normalized pooled dataset did not, so pooling was not appropriate for the normalized dataset. There were no outliers.

Statistics, basis values and estimates are given for OHC2 strength data in Table 5-20. The normalized data and the B-basis values are shown graphically in Figure 5-14.

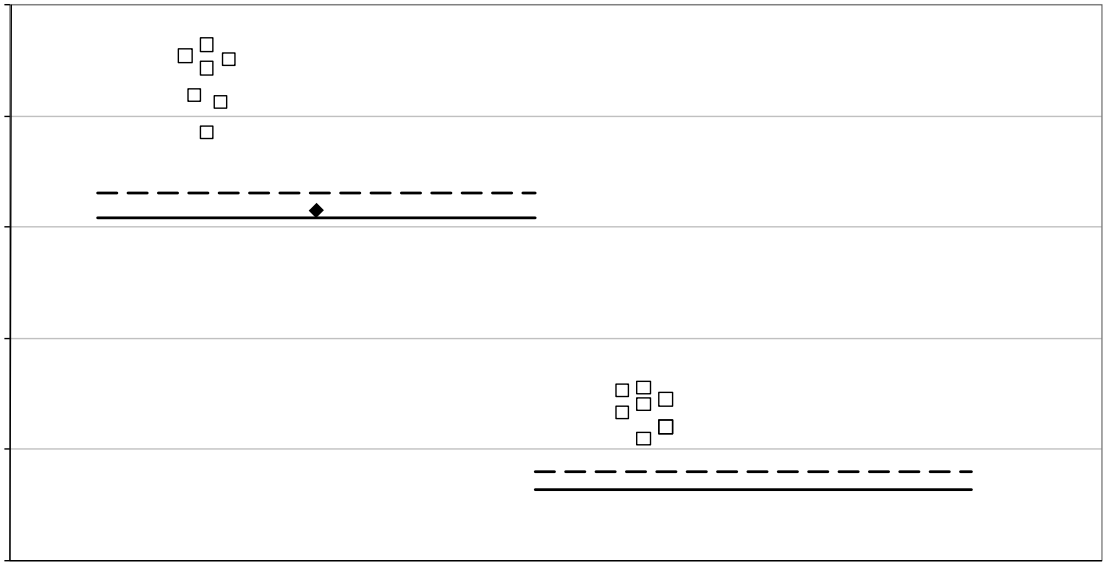

Open-Hole Compression (OHC2) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	40.63	26.41	41.78	27.02
Stdev	2.10	1.22	1.55	0.93
CV	5.17	4.63	3.70	3.43
Modified CV	6.59	6.32	6.00	6.00
Min	35.78	23.56	39.03	25.11
Max	43.23	28.26	43.67	28.67
No. Batches	3	3	3	3
No. Spec.	19	19	19	19
Basis Values and/or Estimates				
B-basis Value	36.54	24.02	39.48	24.72
A-estimate	33.63	22.33	37.91	23.15
Method	Normal	Normal	pooled	pooled
Modified CV Basis Values and/or Estimates				
B-basis Value	35.42	23.16	37.97	23.22
A-estimate	31.72	20.85	35.37	20.61
Method	normal	normal	pooled	pooled

Table 5-20: Statistics and Basis Values for OHC2 Strength data

Open-Hole Compression (OHC3) Strength Basis Values and Statistics				
	Normalized		As Measured	
Env	RTD	ETW	RTD	ETW
Mean	62.78	48.36	64.09	49.32
Stdev	2.34	2.76	2.25	2.45
CV	3.73	5.70	3.51	4.97
Modified CV	6.00	6.85	6.00	6.48
Min	58.95	44.01	60.88	45.74
Max	67.17	54.31	67.57	54.11
No. Batches	3	3	3	3
No. Spec.	19	19	19	19
Basis Values and/or Estimates				
B-basis Value	58.22		59.71	
B-estimate		32.77		34.84
A-estimate	54.98	21.64	56.60	24.50
Method	Normal	ANOVA	Normal	ANOVA
Modified CV Basis Values and/or Estimates				
B-basis Value	56.38	41.96	57.71	42.94
A-estimate	52.01	37.59	53.36	38.58
Method	pooled	pooled	pooled	pooled

5.16 Quasi Isotropic Filled Hole Compression (FHC1)

The FHC1 data had no test failures or outliers. Pooling across environments was acceptable. Statistics, basis values and estimates are given for FHC1 strength data in Table 5-22. The normalized data and the B-basis values are shown graphically in Figure 5-16.

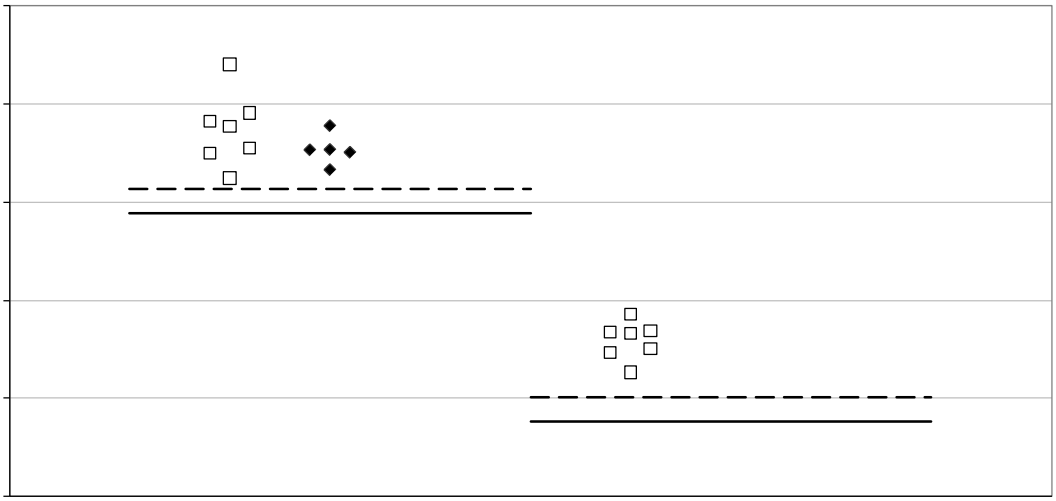

5.17 "Soft" Filled Hole Compression (FHC2)

The FHC2 data had no test failures or outliers. Pooling across environments was acceptable. Statistics, basis values and estimates are given for FHC2 strength data in Table 5-73. The normalized data and the B basis values are shown graphically in Figure 5-17.

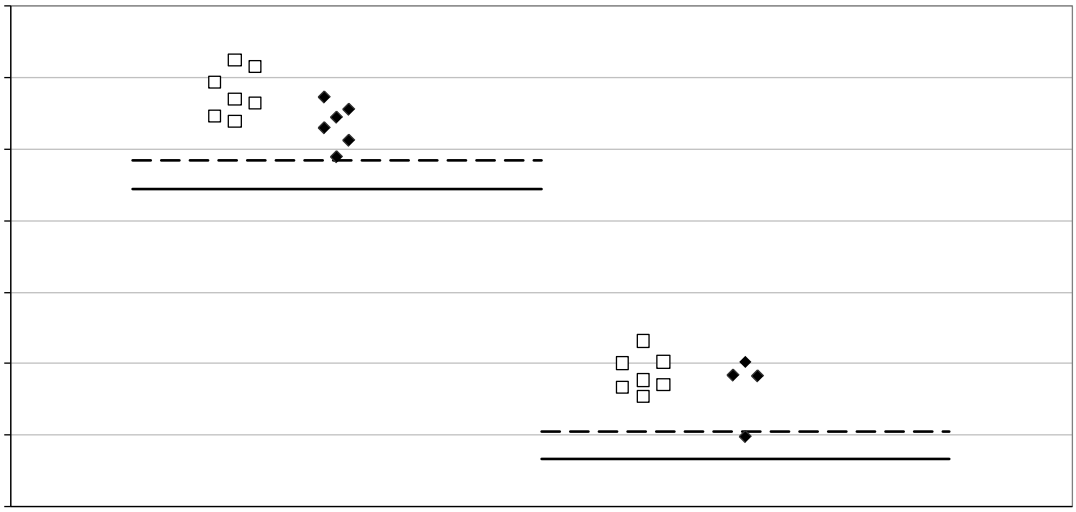

5.18 "Hard" Filled Hole Compression (FHC3)

The as measured data from the RTD environment and the as measured pooled dataset failed the normality test, so pooling was not appropriate for the as measured dataset. The normalized data had no test failures, so pooling was appropriate.

There was one outlier. It was on the low side of batch two of the RTD data. It was an outlier only after pooling the three batches of RTD data. It was an outlier in both the normalized and as measured datasets.

Statistics, basis values and estimates are given for FHC3 strength data in Table 5.18-1. The normalized data and the B basis values are shown graphically in Figure 5.18-1.

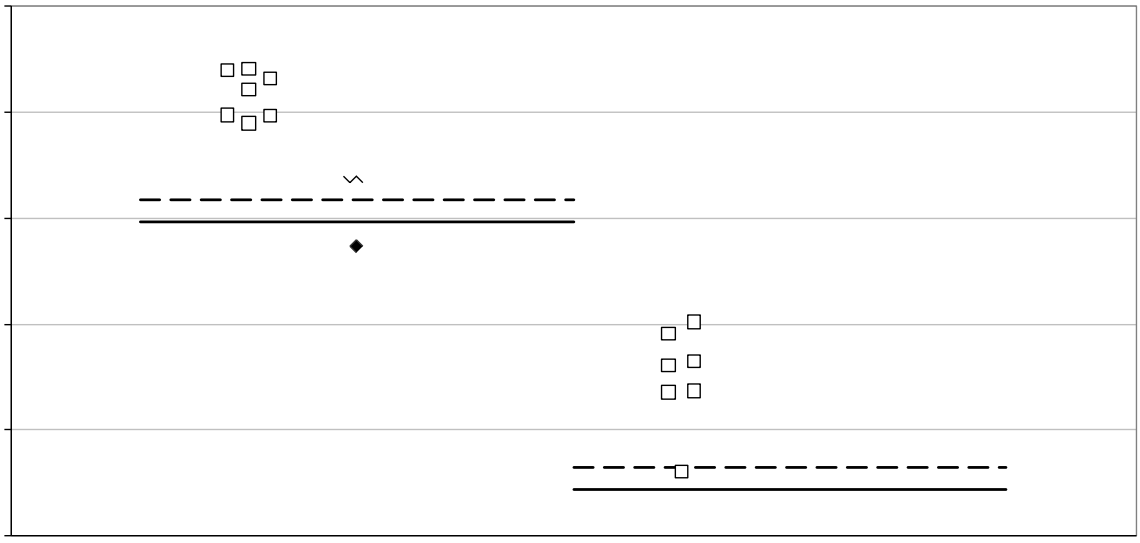

5.19 Laminate Short Beam Shear Strength (LSBS) Data

The Laminate Short Beam Shear data is not normalized. The data from the RTD and ETW conditions failed ADK test for batch-to-batch variation, so only the ANOVA method could be used to compute basis values. Since there are only three batches available, this means that basis values computing using the ANOVA method are estimates only. However, both the RTD and ETW data passed the ADK test with the modified CV transform, so modified CV basis values are provided.

Pooling was not acceptable due to large differences in standard deviations and CV betwet7 C 0 Td [

Env	RTD	ETW
Mean	11.94	6.81
Stdev	0.68	0.21
CV		

5.20 Quasi Isotropic Single Shear Bearing (SSB1)

The as measured

5.21 "Soft" Single Shear Bearing 2 (SSB2)

The SSB2 ETW data for 2% offset strength and ultimate strength, both normalized and as measured, failed the ADK test, which means the ANOVA method was required to compute basis values. Since there are only three batches available, the basis values computed using the ANOVA method are estimates only. The ultimate strength ETW data (both normalized and as measured) passed the ADK test after the modified CV transform was applied. The 2% offset strength data (both normalized and as measured) did not. Modified CV basis values are provided for normalized ultimate strength ETW datasets. Estimates computed using the modified CV method are provided for the 2% offset strength ETW datasets. There were no outliers.

Statistics, basis values and estimates are given for the strength data in Table 5.21-7. The normalized data, B-estimates and B-basis values are shown graphically in Figure 5.21-15

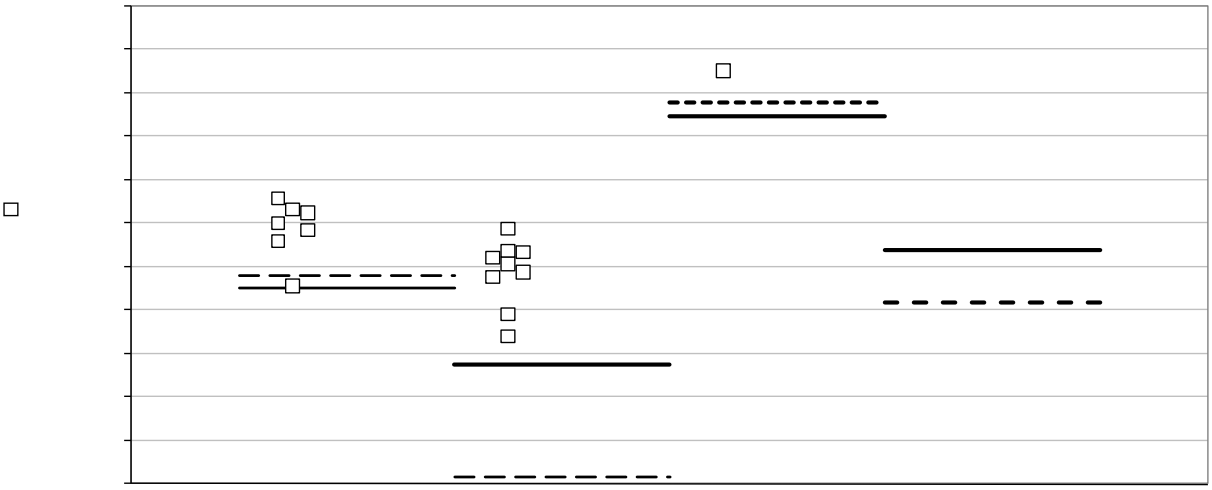

5.22 "Hard" Single Shear Bearing 3 (SSB3)

The pooled dataset for 2% offset strength failed the normality test for both the normalized and as measured datasets, so pooling was not appropriate. However, the as measured 2% pooled dataset passed the normality test after the Mod CV transformation, so pooling was appropriate for the modified CV basis values.

For the normalized RTD 2% offset strength data, the Weibull distribution proved to have the best fit for that data. Modified CV basis values are not available for the normalized RTD 2% offset data due to the non-normality. Pooling the RTD and ETW environments was acceptable for the ultimate strength datasets, both normalized and as measured.

The normalized 2% offset strength ETW data failed both the normality test and the ADK test. The failure of the ADK test means the ANOVA method was required to compute basis values. Since there are only three batches available, the basis values computed using the ANOVA method are estimates only. After applying the modified CV transform to this dataset, it passed the normality test but still failed the ADK test. Estimates computed using the modified CV method are provided for the ETW environment. These are termed estimates due to the dataset failing the ADK test after the transformation for the modified CV method.

There were a total of five outliers in the SSB3 data, two in the 2% offset strength data and three in the ultimate strength data. All five the [(7) 0 Tc 0 Tw [(t)

5.23 Interlaminar Tension and Curved Beam Strength (ILT and CBS)

The ILT and CBS data is not normalized. Basis values are not computed for these properties. However the summary statistics are presented in Table 5-29 and the data are displayed graphically in Figure 5-23.

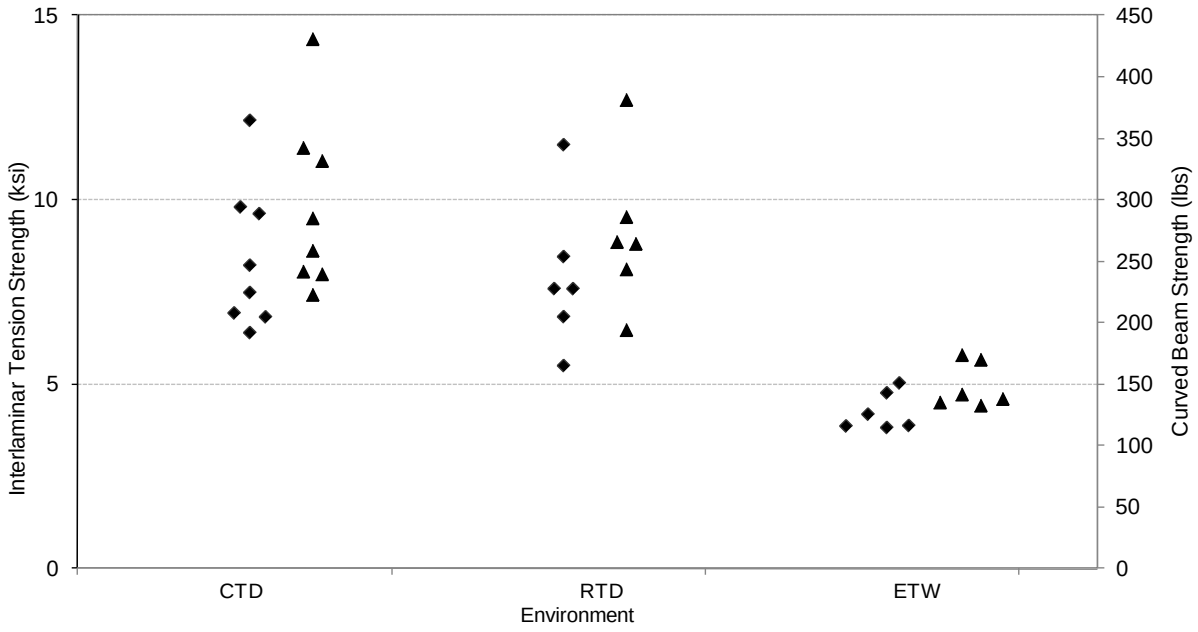

5.24 Compression After Impact (CAI)

Basis values are not computed for these properties. However the summary statistics are presented in Table 5-30 and the data are displayed graphically in Figure 5-24.

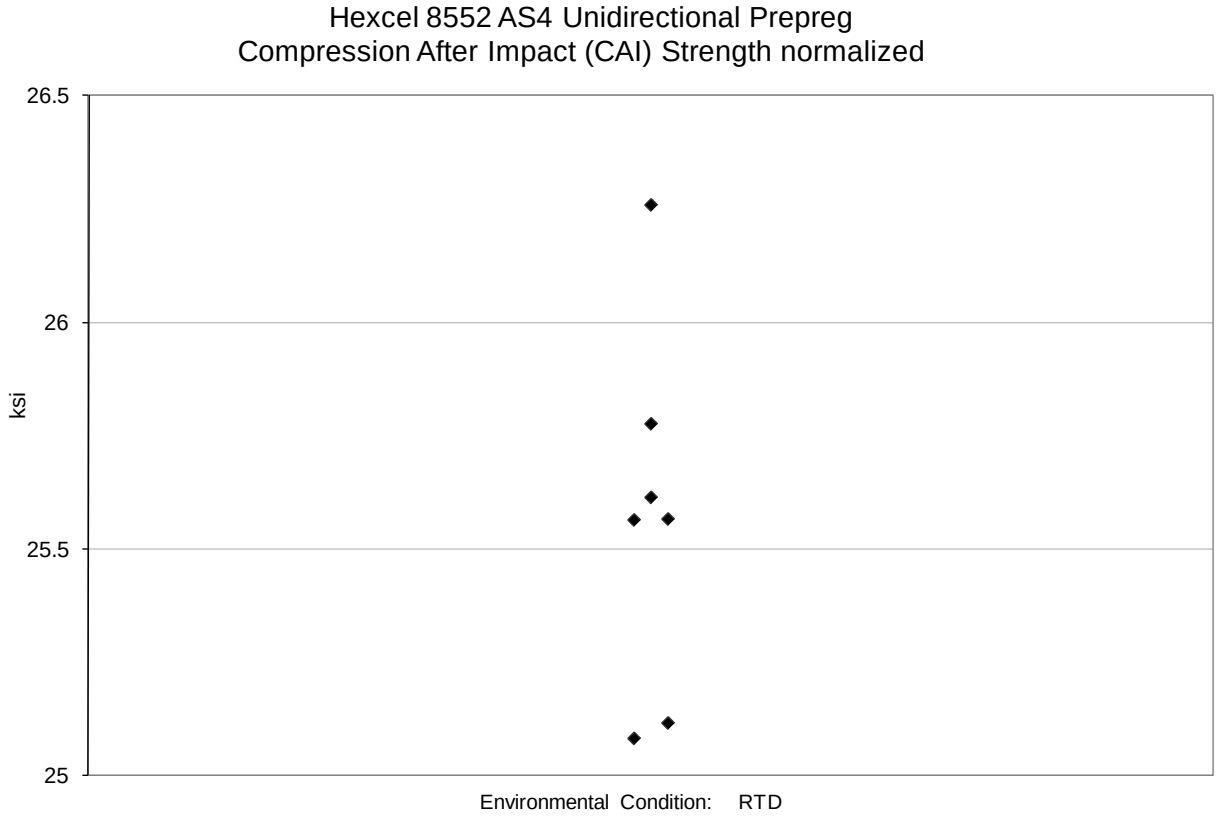

Figure 5-24: Plot for Compression After Impact normalized Strength Data

	Normalized	As Measured
Env	RTD	RTD
Mean	25.57	25.56
Stdev	0.40	0.52
CV	1.57	2.05
Modified CV	6.00	6.00
Min	25.08	24.83
Max	26.26	26.39

Test	Condition	Batch	Specimen Number	Normalized Strength	Strength As Measured	High/ Low	Batch Outlier	Condition Outlier
FHC3	RTD	2	HFU9B215A	87.32	88.21	Low	No	Yes
FHT3	CTD	2	HFU6B116B	64.90	Not an outlier	Low	Yes	No
FHT3	CTD	3	HFU6C118B	Not an outlier	62.20	Low	Yes	No
FHT3	ETW	1	HFU6A11BD	Not an outlier	82.71	High	Yes	No
IPS - 5% Strain	RTD	1	HFUNA211A	NA	12.51	Low	Yes	No
IPS - 5% Strain	RTD	3	HFUNC117A	NA	13.76	Low	Yes	No
LSBS	ETW	1	HFUqA279D	NA	6.63	Low	Yes	No
LT	RTD	2	HFUJB211A	248.112				

7. References

1. Snedecor, G.W. and Cochran, W.G., Statistical Methods, 7th ed., The Iowa State University Press, 1980, pp. 252-253.
2. Stefansky, W., "Rejecting Outliers in Factorial Designs," Technometrics, Vol. 14, 1972, pp. 469-479.
3. Scholz, F.W. and Stephens, M.A., "K-Sample Anderson-Darling Tests of Fit," Journal of the American Statistical Association, Vol. 82, 1987, pp. 918-924.
4. Lehmann, E.L., Testing Statistical Hypotheses, John Wiley & Sons, 1959, pp. 274-275.
5. Levene, H., "Robust Tests for Equality of Variances," in Contributions to Probability and Statistics, ed. I. Olkin, Palo, Alto, CA: Stanford University Press, 1960.
6. Lawless, J.F., Statistical Models and Methods for Lifetime Data, John Wiley & Sons, 1982, pp. 150, 454-460.
7. Metallic Materials and Elements for Aerospace Vehicle Structures, MIL-HDBK-5E, Naval Publications and Forms Center, Philadelphia, Pennsylvania, 1 June 1987, pp. 9-166, 9-167.
8. Hanson, D.L. and Koopmans, L.H., "Tolerance Limits for the Class of Distribution with Increasing Hazard Rates," Annals of Math. Stat., Vol 35, 1964, pp. 1561-1570.
9. Vangel, M.G., "One-Sided Nonparametric Tolerance Limits," Communications in Statistics: Simulation and Computation, Vol. 23, 1994, p. 1137.
10. Vangel, M.G., "New Methods for One-Sided Tolerance Limits for a One-Way Balanced Random Effects ANOVA Model," Technometrics, Vol 34, 1992, pp. 176-185.
11. Odeh, R.E. and Owen, D.B., Tables of Normal Tolerance Limits, Sampling Plans and Screening, Marcel Dekker, 1980.
12. Tomblin, John and Seneviratne, Waruna, Laminate Statistical Allowable Generation for Fiber-Reinforced Composites Material: Lamina Variability Method, U.S. Department of Transportation, Federal Aviation Administration, May 2006.
13. Tomblin, John, Ng, Yeow and Raju, K. Suresh, Material Qualifciation and Equivalency for Polymer Matrix Composite Material Systems: Updated Procedure, U.S. Department of Transportation, Federal Aviation Administration, September 2003.